

# SOĞUK İŞ ÇELIKLERI

## Mevcut Ürün Şekilleri

Uzun Ürünler\*

Levhalar

\* ) Presented data refer exclusively to long products. Please observe the detailed explanations at the end of the data sheet (pdf).

## Ürün Tanımı

BÖHLER K100 is a 12% ledeburitic chromium steel and corresponds to material number 1.2080 (X210Cr12). This commonly used tool steel is highly resistant to abrasive wear. Compared to modern cold work tool steels, BÖHLER K100 has the advantage of simple heat treatment with lower hardening temperatures and single tempering. However, this characteristic tempering behaviour limits the use of advanced coatings.

## Erime rotası

Airmelted

## Özellikler

> Aşınma Direnci : iyi

## Uygulamalar

- > Machine knife (for producers)
- > Fine Blanking, Stamping, Blanking
- > Haddeler
- > Rolling
- > Standard Parts (Molds, Plates, Pins, Punches)
- > Wear parts
- > Cold Forming
- > Geri Dönüşüm Endüstrisi için Parçalar
- > Makine Mühendisliği için Genel Parçalar

## Teknik veriler

Malzeme Tanımı		Standartlar	
1.2080	SEL	4957	EN ISO
~T30403	UNS		
X210Cr12	EN		
~D3	AISI		
~SKD1	JIS		

## Kimyasal Bileşim

C	Si	Mn	Cr
2,00	0,25	0,35	11,50

## Malzeme özellikleri

	Basınç Dayanımı	Isıl işlem sırasında boyutsal kararlılık	Sertlik	Aşındırıcı aşınma direnci	Aşınma direnci yapıştırıcı
BÖHLER K100	★★	★★	★	★★★	★★
BÖHLER K105	★★	★★	★	★★	★★
BÖHLER K107	★★	★★	★	★★★	★★
BÖHLER K110	★★	★★★	★	★★★	★★
BÖHLER K190 MICROCLEAN®	★★★★	★★★★★	★★★★	★★★★	★★★★
BÖHLER K294 MICROCLEAN®	★★★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER K340 ISODUR®	★★★	★★★★	★★★	★★★	★★★★
BÖHLER K340 ECOSTAR®	★★★	★★★	★★	★★	★★
BÖHLER K346	★★★	★★★	★★★	★★★★	★★
BÖHLER K353	★★	★★★	★★	★★	★★
BÖHLER K360 ISODUR®	★★★	★★★★	★★★	★★★★	★★★★
BÖHLER K390 MICROCLEAN®	★★★★★	★★★★★	★★★★	★★★★★	★★★★★
BÖHLER K490 MICROCLEAN®	★★★★	★★★★★	★★★★	★★★★	★★★★
BÖHLER K497 MICROCLEAN®	★★★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER K888 MATRIX	★★★★	★★★★★	★★★★★	★★	★★
BÖHLER K890 MICROCLEAN®	★★★★	★★★★★	★★★★★	★★★	★★★

## Teslimat durumu

## Annealed

Sertlik (HB)

maks. 248

## Air Quenched

## Isıl İşlem

### Annealing

Sıcaklık	800 kadar 850 °C	Slow controlled cooling in furnace at a rate of 50 to 68°F (10 to 20°C/hr) down to approx. (600°C), further cooling in air.
----------	------------------	---


### Stress relieving

Sıcaklık	650 °C	Slow cooling in furnace; intended to relieve stresses set up by extensive machining, or in complex shapes. After through heating, hold in neutral atmosphere for 1-2 hours.
----------	--------	---

### Sertleştirme ve Temperleme

Sıcaklık	940 kadar 970 °C	Oil, salt bath 428 to 482°F or 932 to 1022°F (220 to 250°C or 500 to 550°C), compressed or still air if thickness does not exceed 0,98 inch (25 mm) and if hardening temperature is on the upper side of the range, gas Holding time after temperature equalization: 15 to 30 minutes. After hardening, tempering to the desired working hardness, see tempering chart.
----------	------------------	---

## Tempering chart

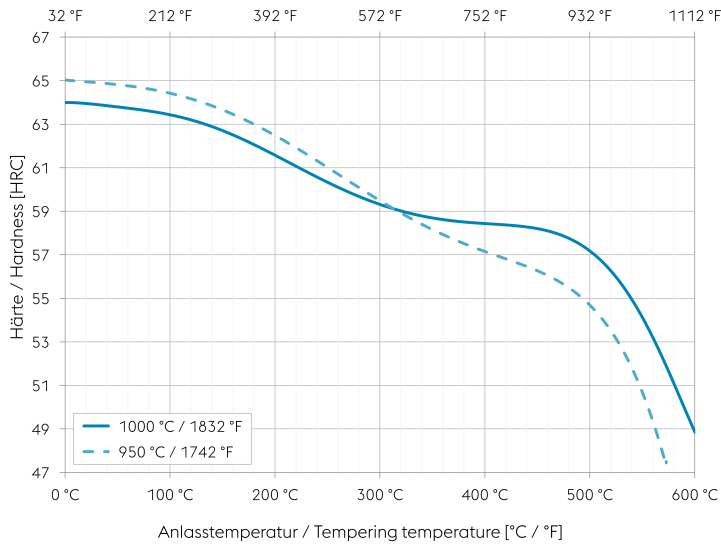

### Tempering:

Specimen size: square 0,787 inch (20 mm)

Slow heating to tempering temperature immediately after hardening.


Time in furnace 1 hour for each 0,787 inch (20 mm) of workpiece thickness but at least 2 hours/cooling in air.

Slow cooling to room temperature after each tempering step is recommended.

Please refer to the tempering chart for guide values for the hardness achievable after tempering.

Tempering for stress relieving 86 to 122 °F (30 to 50 °C) below the highest tempering temperature.


**Continuous cooling CCT curves**

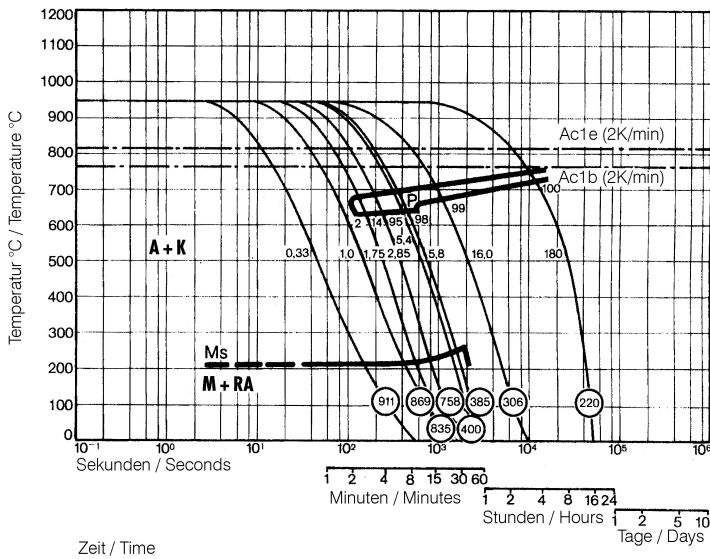

Austenitising temperature: 1742°F (950°C)  
Holding time: 30 minutes

O Vickers hardness  
2...100 phase percentages  
0.33...180 cooling parameter, i.e. duration of cooling from 1472 to 932°F (800 to 500°C) in  $s \times 10^{-2}$   
35,6°F/min (2K/min)... cooling rate in K/min in the 1472 to 932°F (800 to 500°C) range

**Quantitative phase diagram**

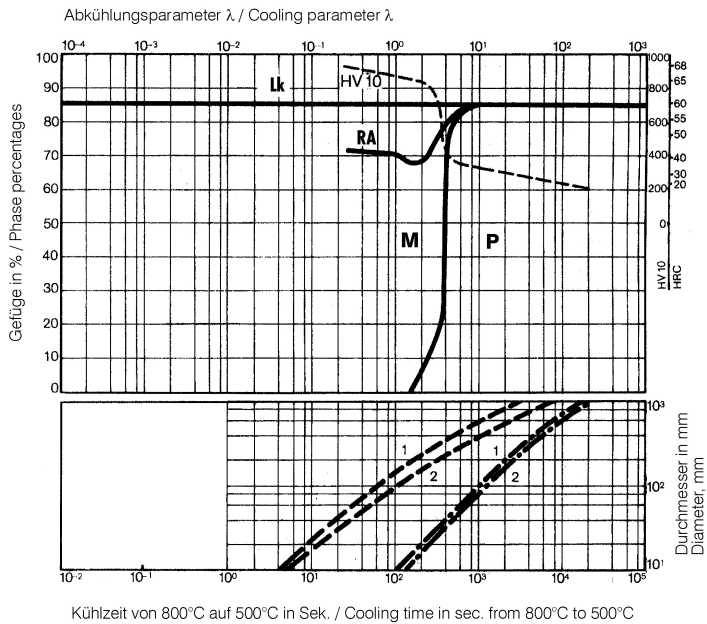


Lk... Ledeburite carbide  
RA... Residual austenite  
A... Austenite  
M... Martensite  
P... Pearlite  
K... Carbide


----- Oil cooling  
- · - Air cooling

1... Edge or face  
2... Core

**Heat treatment sequence**

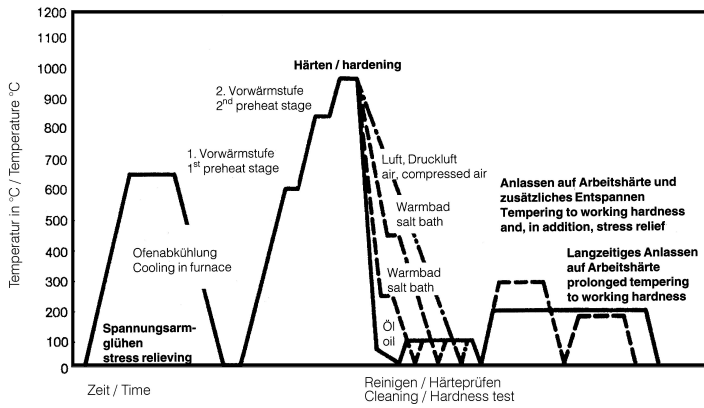


**Isothermal TTT curves**

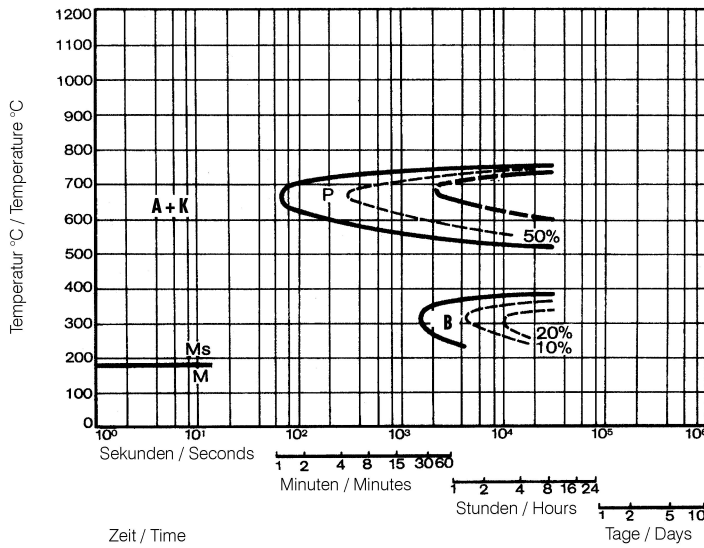

Austenitising temperature: 1742°F (950°C)  
Holding time: 30 minutes

## Influence of work diameter on core hardness and hardness penetration

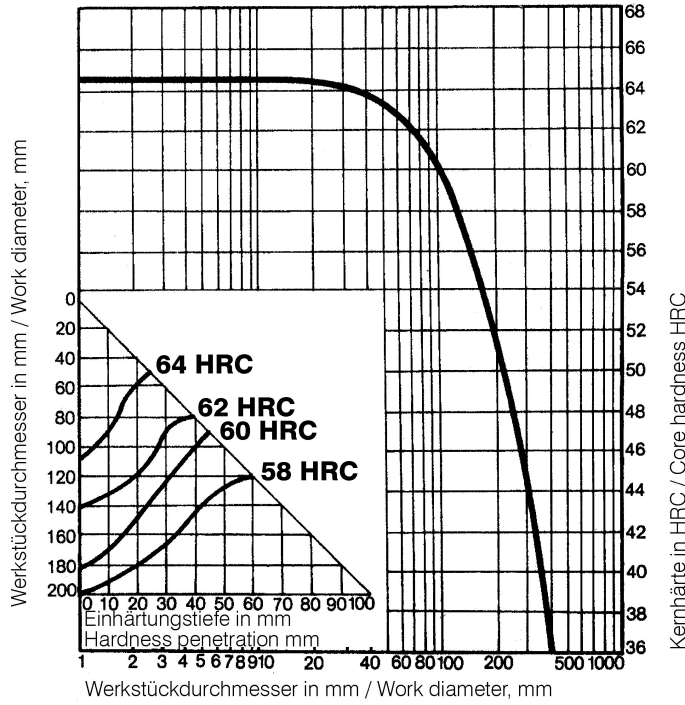

## Fiziksel özellikler

Sıcaklık (°C)	20
Yoğunluk (kg/dm <sup>3</sup> )	7,7
Termal iletkenlik (W/(m.K))	20
Özgül ısı kapasitesi (kJ/kg K)	0,46
Spes. elektrik direnci (Ohm.mm <sup>2</sup> /m)	0,65
Elastikiyet modülü (10 <sup>3</sup> N/mm <sup>2</sup> )	210

## Termal genleşmeler

Sıcaklık (°C)	100	200	300	400	500	600
Termal genleşme (10 <sup>-6</sup> m/(m.K))	10,5	11	11	11,5	12	12

**Long Products:** For additional specifications and technical requirements, please contact our regional voestalpine BÖHLER sales companies.

**Sheet & Plates:** Product Variant may differ in terms of melting process, technical data, delivery, and surface condition as well as available product dimensions. Please contact voestalpine BÖHLER Bleche GmbH & Co KG.

*The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.*

## voestalpine BÖHLER Edelstahl GmbH & Co KG

Mariazeller Straße 25

8605 Kapfenberg, AT

T. +43/50304/20-0

E. info@bohler-edelstahl.at

<https://www.voestalpine.com/bohler-edelstahl/de/>

voestalpine

ONE STEP AHEAD.