

# SICAK İŞ TAKIM ÇELİKLERİ

## Mevcut Ürün Şekilleri

Uzun Ürünler

## Ürün Tanımı

BÖHLER W320 ISODISC is a 3% chromium steel and corresponds to material number 1.2365 (32CrMoV12-28). This tool steel has good hot toughness as well as a very high hot hardness and resistance against heat-checkings. Compared to an X37CrMoV5-1 (material number 1.2343), the steel has an increased molybdenum content, which significantly increases its thermal resistance and thus makes it the ideal material in die closed- and open-doe forging. Due to the lower chromium content, reduced through-hardening occurs which limits its applications to rather smaller tools.

## Erime rotası

Airmelted

## Özellikler

- > Tokluk ve Süneklik : iyi
- > Aşınma Direnci : yüksek
- > İşlenebilirlik : çok yüksek
- > Sıcak Sertlik (kırmızı sertlik) : yüksek
- > Cilalanabilirlik : iyi
- > Mikro temizlik : iyi
- > Termal iletkenlik : çok yüksek

## Uygulamalar

- > Ekstrüzyon
- > Dövme (Sıcak / Yarı Sıcak)
- > Yerçekimi / Düşük Basıncılı Döküm
- > Yüksek Basıncılı Döküm
- > Progressive Forging (Hatebur)

## Teknik veriler

Malzeme Tanımı		Standartlar	
1.2365	SEL	4957	EN ISO
~T20810	UNS	G4404	JIS
32CrMoV12-28	EN		
~H10	AISI		
SKD7	JIS		

## Kimyasal Bileşim

C	Si	Mn	Cr	Mo	V
0,31	0,30	0,35	2,90	2,70	0,50

## Malzeme özellikleri

	Sıcak güç	Sıcak tokluk	Sıcak aşınma direnci
	★★★	★★	★★★
	★★	★★★	★★
	★★	★★★★★	★★
	★★★	★★★	★★★
	★★★	★★★★★	★★★
	★★★★★	★★★	★★★★★
	★★★	★★★★★	★★★
	★★★★★	★★★★★	★★★★★
	★★	★★★★★	★★
	★★★★★	★★★★★	★★★★★

## Teslimat durumu

### Annealed

Sertlik (HB)	maks. 229
--------------	-----------

## Isıl işlem

### Annealing

Sıcaklık	750 kadar 800 °C	Holding time 6 to 8 hours. Slow, controlled furnace cooling at 10 to 20°C/h (50 to 68 °F/hr) to approx. 600°C (1112°F), further cooling in air.
----------	------------------	---


### Stress relieving

Sıcaklık	600 kadar 670 °C	For stress relief after extensive machining or for complicated tools. Holding time depending on tool size after complete heating 2 - 6 hours in neutral atmosphere. Slow furnace cooling.
----------	------------------	---


### Sertleştirme ve Temperleme

Sıcaklık	1.010 kadar 1.050 °C	Holding time after temperature equalization: 15 to 30 minutes; Quenching: Oil, salt bath (500 - 550°C [932-1022°F]), air, vacuum; After hardening, tempering to the desired working hardness (see tempering chart).
----------	----------------------	---

## Heat treatment sequence

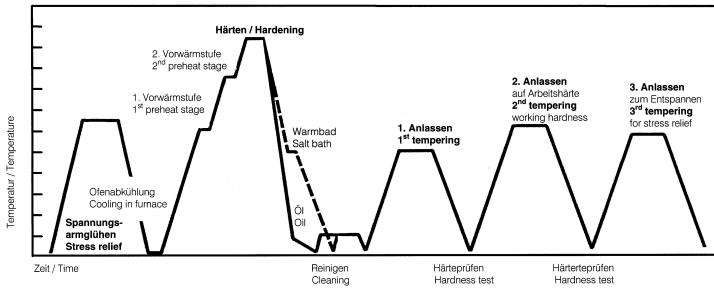


## Continuous cooling CCT curves

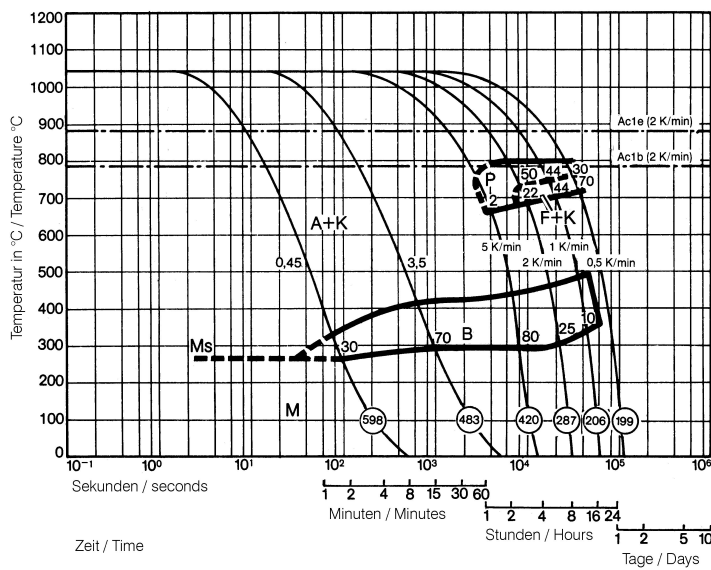

Austenitising temperature: 1886°F (1030°C)  
Holding time: 15 minutes

O Vickers hardness  
2...80 phase percentages  
0.45...3.5 cooling parameter, i.e. duration of cooling from 1472-932°F (800 - 500°C) in  $s \times 10^{-2}$   
41...32.9°F/min (5...0.5 K/min) cooling rate in °F/min (K/min) in the 1472-932°F (800 - 500°C) range

**Quantitative phase diagram**

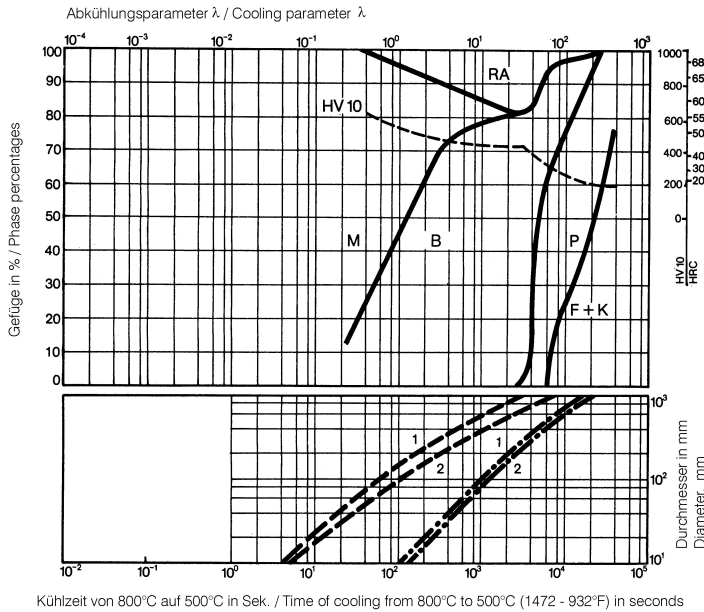


A... Austenite  
B... Bainite  
F... Ferrite  
K... Carbide  
M... Martensite  
P... Pearlite  
RA... Retained austenite

----- Oil cooling  
- · - Air cooling

1... Edge or face  
2... Core

**Tempering chart**

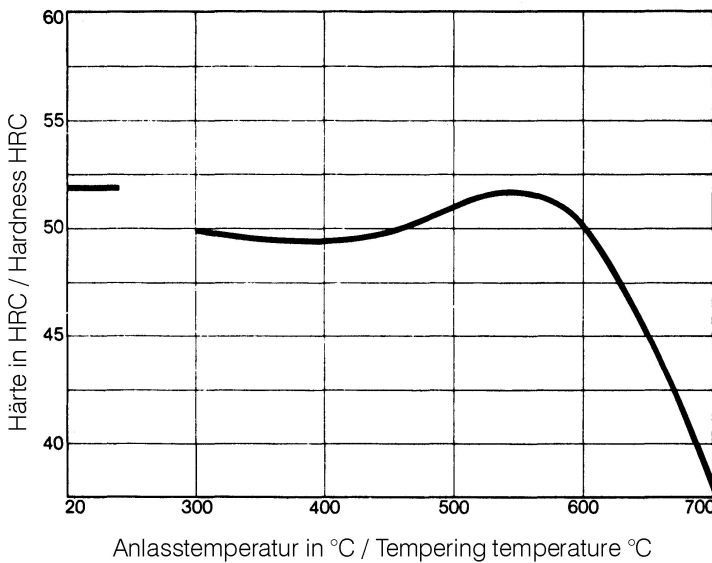

**Tempering:**

Slow heating to tempering temperature immediately after hardening / time in furnace 1 hour for each 0,787 inch (20 mm) of work piece thickness but at least 2 hours / cooling in air. It is recommended to temper at least twice. A third tempering cycle for the purpose of stress relieving may be advantageous.


1st tempering approx. 30°C (86°F) above maximum secondary hardness.

2nd tempering to desired working hardness.

The tempering chart shows average tempered hardness values.

3rd for stress relieving at a temperature 86 to 122°F (30 - 50°C) below highest tempering temperature.

## Hot strength chart

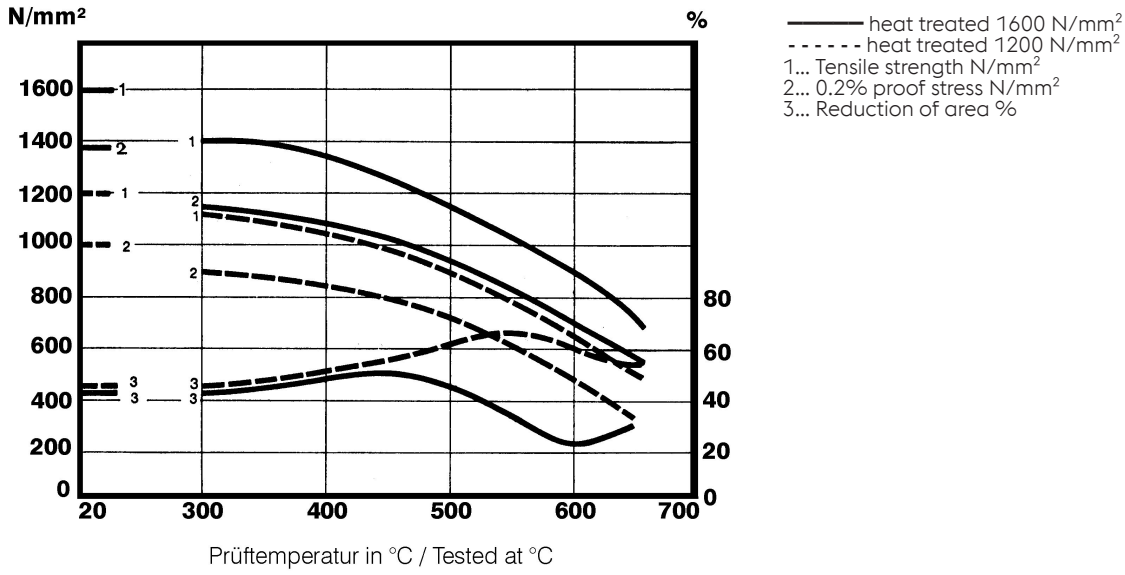

## Fiziksel özellikler

Sıcaklık (°C)	20
Yoğunluk (kg/dm <sup>3</sup> )	7,85
Termal iletkenlik (W/(m.K))	30
Özgül ısı kapasitesi (kJ/kg K)	0,46
Spes. elektrik direnci (Ohm.mm <sup>2</sup> /m)	0,37
Elastikiyet modülü (10 <sup>3</sup> N/mm <sup>2</sup> )	215

## Termal genleşmeler

Sıcaklık (°C)	100	200	300	400	500	600	700
Termal genleşme (10 <sup>-6</sup> m/(m.K))	12	12,5	12,7	13	13,2	13,4	13,7

For additional specifications and technical requirements, please contact our regional voestalpine BÖHLER sales companies.

*The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.*

voestalpine BÖHLER Edeltahl GmbH & Co KG  
 Mariazeller Straße 25  
 8605 Kapfenberg, AT  
 T. +43/50304/20-0  
 E. info@bohler-edeltahl.at  
<https://www.voestalpine.com/bohler-edeltahl/de/>

voestalpine

ONE STEP AHEAD.